

Hidden constant in the anomalous Hall effect of high-purity magnet MnSi

 Minhyea Lee,¹ Y. Onose,¹ Y. Tokura,^{2,3} and N. P. Ong¹
¹*Department of Physics, Princeton University, Princeton, New Jersey 08544, USA*
²*Department of Applied Physics, University of Tokyo, Tokyo 113-8656, Japan*
³*ERATO, JST, Spin Superstructure Project (SSS), Tsukuba 305-8562, Japan*

(Received 27 October 2006; revised manuscript received 14 December 2006; published 7 May 2007)

Measurements of the Hall conductivity in MnSi can provide incisive tests of theories of the anomalous Hall (AH) effect, because both the mean free path and magnetoresistance (MR) are unusually large for a ferromagnet. The large MR provides an accurate way to separate the AH conductivity σ_{xy}^A from the ordinary Hall conductivity σ_{xy}^N . Below the Curie temperature T_C , σ_{xy}^A is linearly proportional to M (magnetization) with a proportionality constant S_H that is independent of both T and H . In particular, S_H remains a constant while σ_{xy}^N changes by a factor of 100 between 5 K and T_C . We discuss implications of the hidden constancy in S_H .

 DOI: [10.1103/PhysRevB.75.172403](https://doi.org/10.1103/PhysRevB.75.172403)

PACS number(s): 75.47.Np, 75.30.-m, 71.27.+a

The origin of the anomalous Hall (AH) effect in ferromagnets has been vigorously debated for the past 50 years. Karplus and Luttinger¹ (KL) proposed in 1954 that the AH current is an intrinsic current that is independent of the mean free path ℓ .²⁻⁵ In the competing skew-scattering theory, the AH current arises from asymmetric scattering off impurities and defects, and is proportional to ℓ .⁶ While older experiments favor skew scattering, support for the KL/Berry-phase theory has been obtained from recent experiments.⁷⁻¹² However, uncertainty remains on the relative importance of the two AH currents in pure systems (intrinsic regime) and on the role of extrinsic effects (impurities). Here, we show that the AH effect in a high-purity ferromagnet MnSi reveals a remarkable constancy. At temperatures $T < T_C$, the AH conductivity σ_{xy}^A is strictly proportional to M with a proportionality constant S_H that is independent of both T and magnetic field \mathbf{H} .

Conventionally, the observed Hall resistivity ρ_{yx} in a ferromagnet is written empirically as¹³

$$\rho_{yx} = R_0 B + \mu_0 R_s M, \quad (1)$$

where R_0 is the ordinary Hall coefficient, μ_0 the permeability, and $\mathbf{B} = \mu_0(\mathbf{H} + \mathbf{M})$ the induction field. The ‘‘anomalous Hall coefficient’’ $R_s(T)$ is a scale factor that matches the M - H curve to the anomalous part of the Hall resistivity $\rho'_{yx} \equiv \rho_{yx} - R_0 B$. As such, $R_s(T)$ must be independent of the field B . AH measurements are routinely reported as a plot of $R_s(T)$ vs T as an empirical parameter. Yet, Eq. (1) has never been justified microscopically.

To distinguish between the two theories, we have focused on the intrinsic AH signal found in high-purity ferromagnets. In these systems, with large magnetoresistance (MR), the difficulties with Eq. (1) become acute. Additivity of currents in a solid implies that the total Hall conductivity is the sum $\sigma_{xy} = \sigma_{xy}^N + \sigma_{xy}^A$, where σ_{xy}^N is the ordinary Hall conductivity. Additivity also requires that σ_{xy}^A be proportional to M ,¹¹⁻¹⁵ which we express as

$$\sigma_{xy}^A = S_H M. \quad (2)$$

The scale factor S_H plays the central role in our analysis. Converting σ_{xy} to ρ_{yx} , we have

$$\rho_{yx} = R_0 B + S_H \rho^2 M, \quad (3)$$

with ρ the resistivity and $R_0 = \sigma_{xy}^N \rho^2 / B$ (we assume that $\rho_{yx} \ll \rho$). We remark that Eq. (3) goes beyond just taking R_s to be ρ dependent (see, e.g., Ref. 16). When ρ varies strongly with H , M fails to match ρ'_{yx} altogether, and R_s cannot be either defined or measured. This is especially so when ℓ changes greatly with T and H . As we show, focusing on S_H uncovers the proper scaling between M and the AH response.

The metal MnSi, which displays one of the highest conductivities in a ferromagnet, has drawn intense interest because it exhibits non-Fermi-liquid behavior at applied pressures above 14 kbar.^{17,18} Under hydrostatic pressure, it turns out that the Hall effect is indeed highly sensitive to the helical spin configuration, as discussed elsewhere.¹⁹ At ambient pressure and zero H , MnSi undergoes a transition at $T_C = 30$ K to a helical magnetic state with a long pitch λ (~ 180 Å).²⁰ Neutron-scattering experiments have established that, in a weak field ($H < 0.1$ T), the spins cant toward the direction of \mathbf{H} to assume a conical structure and eventually align at $H \sim 0.6$ T.^{21,22}

The MnSi crystals were grown by the floating-zone method. Three crystals of area of 2×1 mm² and thickness of 50–80 μm were measured. At 4 K, values of ρ range from 0.4 to 5 $\mu\Omega$ cm. The residual resistivity ratio varies from 40 to 80. Contacts with contact resistance ≤ 1 Ω were made with Ag epoxy. Hall measurements were performed with the current (5 mA) applied parallel to the longest side (x axis), the field \mathbf{H} parallel to the shortest side (z axis), and Hall E field measured along \hat{y} . With field-sweep rates of 0.05–0.1 T/min, we can resolve changes of ~ 2 n Ω cm in ρ_{yx} at low T . M is measured in a superconducting quantum interference device (SQUID) magnetometer. Above 2 K, hysteretic behavior is not observed.

As shown in the magnetization curves [Fig. 1(a)], the conical angle rapidly closes with field to produce the initial linear increase in M . The kink at $H_k \sim 0.6$ T corresponds to alignment of the moments along \mathbf{H} .

Between T_C and 4 K, ρ in zero H decreases by a factor of 10. As shown below, this is entirely due to an increase in ℓ (which reaches ~ 240 Å at 4 K). Figure 1(b) shows that the MR is large ($\sim 40\%$ near T_C , decreasing to 17% at 10 K at

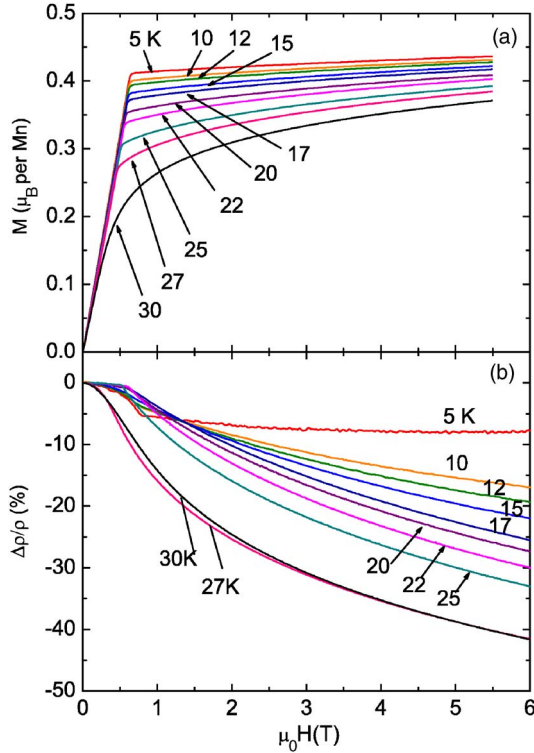


FIG. 1. (Color online) The magnetization curves M vs H [panel (a)] and curves of the relative magnetoresistance $\Delta\rho/\rho$ [panel (b)] in MnSi at selected $T \leq T_C$ (30 K). Below T_C in panel (a), the linear increase in M up to the kink field H_k reflects the canting of the moments toward \mathbf{H} . In panel (b), the MR becomes large (40%) as $T \rightarrow T_C$. Above H_k , M displays a negative curvature (especially near T_C), whereas the curvature in $\Delta\rho/\rho$ is positive.

6 T). The large changes in ρ with T and H make MnSi ideal for investigating how the intrinsic AH signal changes with carrier scattering time.

Curves of ρ_{yx} vs H are shown in Fig. 2 for T from 5 to 200 K. Above 150 K, ρ_{yx} is linear in H , consistent with holelike carriers ($\sigma_{xy} > 0$ and thus $\rho_{yx} > 0$). As T decreases below 50 K, however, ρ_{yx} develops strong curvature in weak H . Below T_C , ρ_{yx} acquires an AH term that, at first glance, seems to resemble M in accordance with Eq. (1). However, a more direct comparison reveals that the M - H curves cannot be scaled to fit the curves of ρ'_{yx} . The reason is their opposite curvatures. The curvature of M is negative above H_k , whereas ρ'_{yx} displays positive curvature [Fig. 2(b)]. The sign difference in the curvatures precludes definitively any satisfactory fit to Eq. (1).

Our approach is as follows. If Eq. (3) is correct, at each $T < T_C$, the profile of ρ'_{yx} vs H must match that of $\rho^2 M$ vs H (S_H is taken to be H independent). In this regard, it is reassuring that, unlike M , the product $\rho^2 M$ shares the same curvature as ρ'_{yx} . By varying the parameters R_0 and S_H , we succeed in obtaining close fits at each T , as shown in Fig. 2(b). The close match at each T provides strong evidence for the validity of Eq. (3). With R_0 and S_H determined, the two Hall conductivities may be separated at each T (see below).

We have also searched for a skew-scattering contribution by adding an AH conductivity that scales as M and is

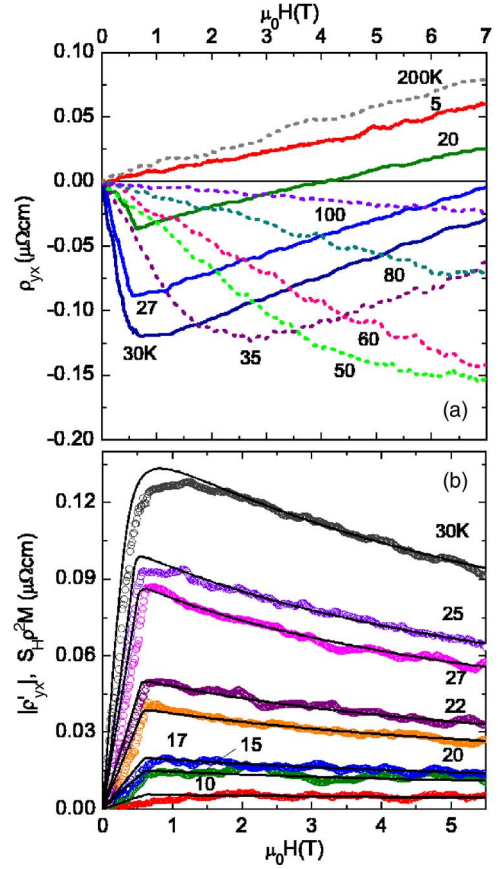


FIG. 2. (Color online) The *observed* Hall resistivity ρ_{yx} in MnSi at selected T [5–200 K, panel (a)] and the fit of the anomalous part ρ'_{yx} to the modified magnetization profile $\rho^2 M$ below T_C [panel (b)]. Panel (a) shows that ρ_{yx} is linear in H at high T , but gradually acquires an anomalous component $\rho'_{yx} = \rho_{yx} - R_0 B$ with a prominent “knee” feature below T_C . In panel (b), at each T , ρ'_{yx} (open circles) is fitted to the profile of $\rho^2 M$ (solid curves), treating S_H and R_0 as adjustable H -independent parameters. Note the positive curvature of the high-field segments.

linear in ℓ . We write $\sigma_{xy}^{sk} = \alpha S_H M \rho(0) / \rho(H)$, where the dimensionless parameter $\alpha(T)$ defines its magnitude at $H=0$ relative to the KL term, and $\rho(0) / \rho(H)$ gives the H dependence of ℓ . In Eq. (3), the second term is amended to $S_H M \rho(H)^2 [1 + \alpha \rho(0) / \rho(H)]$. We found that including α did not improve the fits. Optimization leads to values of α that fluctuate from 0 to 0.05 with no discernible trend (and consistent with $\alpha=0$).

As a consistency check, we note that the fits are physically meaningful only if both parameters turn out to vary only weakly with T , if at all. The variations of R_0 and S_H obtained from the fits are plotted against T in Fig. 3. Within the scatter, the two parameters are virtually independent of T . The inferred R_0 is nearly unchanged as T decreases from T_C to 5 K, despite the tenfold decrease in ρ . This verifies our starting assumption that the decrease in ρ comes entirely from the increase in ℓ , possibly reflecting suppression of scattering from spin fluctuations. From the Fermi wave vector $k_F \sim 1.36 \times 10^8 \text{ cm}^{-1}$, we find that the parameter $k_F \ell$ varies from 330 to 30 between 4 K and T_C .

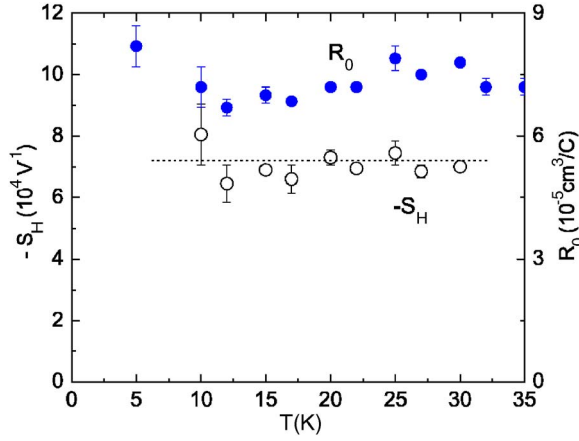


FIG. 3. (Color online) Values of the scale factor S_H (open circles) and the ordinary Hall coefficient R_0 (solid circles) obtained from the fits shown in Fig. 2(b). The average of S_H (dashed line) has the value $-(7.06 \pm 0.48) \times 10^4 \text{ V}^{-1}$. The average R_0 gives a Hall density $n_H = (8.53 \pm 0.07) \times 10^{22} \text{ cm}^{-3}$ and $k_F \approx 1.36 \times 10^8 \text{ cm}^{-1}$ in the Sommerfeld approximation.

The constancy of S_H in Fig. 3 is more interesting and significant. As T decreases below T_C , both the magnetization and resistivity vary strongly with both H and T . Nonetheless, the AH conductivity is completely determined by $M(T, H)$, as expressed in Eq. (2). The constancy of S_H implies that the dependence of σ_{xy}^A on T (or H) derives entirely from that of $M(T, H)$. In particular, the tenfold change in ℓ below T_C has no observable effect on σ_{xy}^A . The task of predicting the AH conductivity in MnSi has been reduced to calculating one constant, S_H . This situation is in marked contrast to that presented by an analysis based on $R_s(T)$ [Eq. (1)].

It is instructive to compare directly the anomalous and ordinary Hall conductivities (Fig. 4). As the latter [calculated as $\sigma_{xy}^N = R_0 B / \rho(H)^2$] increases as $\sim \ell^2 H$, it greatly exceeds the former in magnitude at low T . The two Hall conductivities are plotted in Fig. 4 with the field fixed at 1 T. As mentioned, below T_C , σ_{xy}^A strictly follows the T dependence of M (solid curve) and is insensitive to the steep increase in ℓ (the dashed curve shows the conductivity σ). At 5 K, σ_{xy}^A attains the value $240 (\Omega \text{ cm})^{-1}$. By contrast, σ_{xy}^N is initially 20 times weaker than the AH term at T_C , but increases a 100-fold as $T \rightarrow 5 \text{ K}$ and thus, ρ'_{yx} was not able to be detected in Fig. 2.

Our finding that σ_{xy}^A is nearly T independent disagrees with Ref. 14 which reports a strong deviation toward zero as T decreases to 5 K. Our conjecture for the discrepancy is that the quantity plotted in Fig. 5 of Ref. 14 is actually the absolute value of the total Hall conductivity $|\sigma_{xy}| = |\frac{\rho_{yx}}{\rho^2}|$ (at a fixed field $H=0.1 \text{ T}$), rather than σ_{xy}^A . Between 30 and 5 K, ρ_{yx} measured at 0.1 T falls toward zero as $T \rightarrow 5 \text{ K}$ (see Fig. 2 here), which implies that the total σ_{xy} does the same. It seems crucial to separate out the ordinary Hall current in MnSi. Another speculation for the discrepancy is that at the low field of $H=0.1 \text{ T}$ as in Ref. 14, the contribution of the magnetization to AH effect in MnSi may be nontrivial due to its helical nature. Thus, its contribution to ρ_{yx} can be different from that of fully ferromagnetic state in $H > 0.6 \text{ T}$, as we observed under hydrostatic pressure.¹⁹

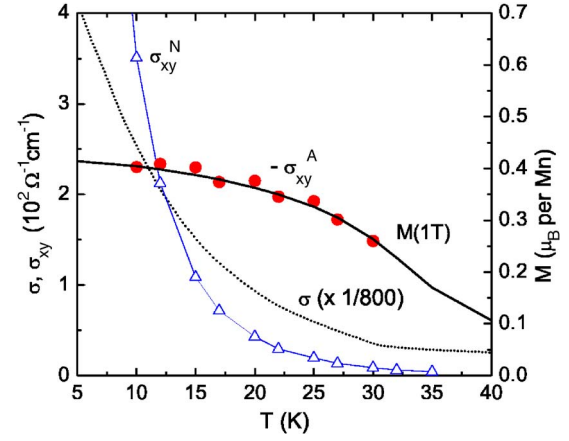


FIG. 4. (Color online) Comparison of the AH conductivity σ_{xy}^A (solid circles) with the ordinary Hall conductivity σ_{xy}^N (open triangles) in a 1 T field (they have opposite signs). σ_{xy}^A is obtained from Eq. (2) using S_H shown in Fig. 3 and the measured M (solid curve), whereas $\sigma_{xy}^N \sim \ell^2$ is calculated from R_0 . As shown, σ_{xy}^A is strictly independent of ℓ ; it changes slowly with T only because $M(T)$ does. The T dependence of the conductivity $\sigma \sim \ell$ (dashed curve) reflects ℓ vs T .

The relationship between the KL term and the Berry phase has been discussed by several groups.²⁻⁵ The curl of the Berry potential leads to an effective magnetic field $\mathbf{\Omega}(\mathbf{k})$ in \mathbf{k} space that adds a new term to the group velocity, viz. (see Ref. 23 for an elementary treatment),

$$\hbar \mathbf{v}(\mathbf{k}) = \nabla_{\mathbf{k}} \epsilon(\mathbf{k}) + e \mathbf{\Omega}(\mathbf{k}) \times \mathbf{E}. \quad (4)$$

The anomalous term $e \mathbf{\Omega} \times \mathbf{E}$, which is transverse to \mathbf{E} , then gives a Hall conductivity that is independent of ℓ (i.e., dissipationless).

The results in Fig. 4 showing that σ_{xy}^A is insensitive to the tenfold change in ℓ from 5 K to T_C provide compelling evidence in favor of the KL theory (and its Berry-phase-based versions). However, present theories do not account for the broad interval of T over which σ_{xy}^A remains ℓ independent. How ubiquitous the constancy is (at low T) in other ferromagnetic systems¹⁵ and how it is modified at higher T are issues for further investigation (for, e.g., in some ferromagnets, ρ'_{yx} changes sign near T_C).

The experiment also addresses the relative importance of skew scattering compared to the KL term.²⁴⁻²⁶ In recent calculations, the skew-scattering term is either comparable to the KL term²⁵ or strongly dominant when $k_{so} \ell > 1$, where $k_{so} = E_{so} / v_F$, with E_{so} and v_F the energy scale of spin-orbit interaction and Fermi velocity, respectively.²⁶ When the skew term is included, there is apparently no regime in which the KL term is clearly dominant (i.e., σ_{xy}^A strictly independent of ℓ).

By contrast, our results on MnSi show that, at all $T < T_C$, σ_{xy}^{sk} is essentially unresolved and σ_{xy}^A is consistent with the KL term throughout the interval $30 < k_F \ell < 330$. In our experimental results, σ_{xy}^A still remains constant at $T < T_C$. This disagreement suggests either that skew scattering may have been greatly overestimated or that inelastic scattering may play a role at finite temperature.²⁷

Further understanding of the intrinsic AH conductivity requires measurements in high-purity crystals with large $k_F\ell$ (in thin-film samples, extrinsic scattering from the surface is problematic). We show that additivity of Hall currents provides the correct perspective to reconcile the large MR with the scaling between the AH current with M . The analysis allows R_0 (hence σ_{xy}^N) to be isolated. More significantly, it uncovers a scaling factor S_H that is independent of both H and T below T_C . The skew-scattering contribution is

negligibly small (0-5%). The constancy of S_H implies the AH current is completely determined by the curves of M vs H below T_C . This simple scaling is obscured if ρ'_{yx} is forced to fit M in order to extract R_s , or if samples with large extrinsic scattering are used.

We have benefited from useful discussions with N. Nagaosa and S. Onoda. Research at Princeton University was supported by the U.S. National Science Foundation (DMR-0213706).

-
- ¹R. Karplus and J. M. Luttinger, *Phys. Rev.* **95**, 1154 (1954).
²G. Sundaram and Q. Niu, *Phys. Rev. B* **59**, 14915 (1999).
³M. Onoda and N. Nagaosa, *J. Phys. Soc. Jpn.* **71**, 19 (2002).
⁴T. Jungwirth, Q. Niu, and A. H. MacDonald, *Phys. Rev. Lett.* **88**, 207208 (2002); Y. Yao, L. Kleinman, A. H. MacDonald, J. Sinova, T. Jungwirth, D. S. Wang, E. Wang, and Q. Niu, *ibid.* **92**, 037204 (2004).
⁵F. D. M. Haldane, *Phys. Rev. Lett.* **93**, 206602 (2004).
⁶J. Smit, *Physica (Amsterdam)* **21**, 877 (1955).
⁷P. Matl, N. P. Ong, Y. F. Yan, Y. Q. Li, D. Studebaker, T. Baum, and G. Doubinina, *Phys. Rev. B* **57**, 10248 (1998).
⁸Y. Taguchi, Y. Oohara, H. Yoshizawa, N. Nagaosa, and Y. Tokura, *Science* **291**, 2573 (2001).
⁹W.-L. Lee, S. Watauchi, V. L. Miller, R. J. Cava, and N. P. Ong, *Science* **303**, 1647 (2004).
¹⁰R. Mathieu, A. Asamitsu, H. Yamada, K. S. Takahashi, M. Kawasaki, Z. Fang, N. Nagaosa, and Y. Tokura, *Phys. Rev. Lett.* **93**, 016602 (2004).
¹¹C. Zeng, Y. Yao, Q. Niu, and H. H. Weitering, *Phys. Rev. Lett.* **96**, 037204 (2004).
¹²Y. Onose and Y. Tokura, *Phys. Rev. B* **73**, 174421 (2006).
¹³C. Hurd, *The Hall Effect in Metals and Alloys* (Plenum, New York, 1972), Chap. 5, pp. 153–182.
¹⁴N. Manyala, Y. Sidis, J. F. Ditusa, G. Aeppli, D. P. Young, and Z. Fisk, *Nat. Mater.* **3**, 255 (2004).
¹⁵A. Husmann and L. J. Singh, *Phys. Rev. B* **73**, 172417 (2006).
¹⁶Y. Kats, I. Genish, L. Klein, J. W. Reiner, and M. R. Beasley, *Phys. Rev. B* **70**, 180407 (2004); J. Kötztler and W. Gil, *ibid.* **72**, 060412(R) (2005).
¹⁷C. Pfeleiderer, G. J. McMullan, S. R. Julian, and G. G. Lonzarich, *Phys. Rev. B* **55**, 8330 (1998).
¹⁸C. Pfeleiderer, S. R. Julien, and G. G. Lonzarich, *Nature (London)* **414**, 427 (2001).
¹⁹Minhyea Lee, W. Kang, Y. Onose, and N. P. Ong (unpublished).
²⁰Y. Ishikawa, Y. Noda, Y. J. Uemura, C. F. Majkrzak, and G. Shirane, *Phys. Rev. B* **31**, 5884 (1985).
²¹Y. Ishikawa and M. Arai, *J. Phys. Soc. Jpn.* **53**, 2726 (1984).
²²C. Thessieu, C. Pfeleiderer, A. N. Stepanov, and J. Flouquet, *J. Phys.: Condens. Matter* **9**, 6677 (1997).
²³N. P Ong and W.-L. Lee, arXiv:cond-mat/0508236 (unpublished).
²⁴P. Nozières and C. Lewiner, *J. Phys. (France)* **34**, 901 (1973).
²⁵V. K. Dugaev, P. Bruno, M. Taillefumier, B. Canals, and C. Lacroix, *Phys. Rev. B* **71**, 224423 (2005).
²⁶S. Onoda, N. Sugimoto, and N. Nagaosa, *Phys. Rev. Lett.* **97**, 126602 (2006).
²⁷S. Onoda and N. Nagaosa (private communication).